

## Bubbles versus biofilms: a novel method for the removal of marine biofilms attached on antifouling coatings using an ultrasonically activated water stream

This content has been downloaded from IOPscience. Please scroll down to see the full text.

2016 Surf. Topogr.: Metrol. Prop. 4 034009

(<http://iopscience.iop.org/2051-672X/4/3/034009>)

View [the table of contents for this issue](#), or go to the [journal homepage](#) for more

### Download details:

IP Address: 89.202.245.164

This content was downloaded on 20/09/2016 at 12:33

Please note that [terms and conditions apply](#).

You may also be interested in:

[A comparison of ultrasonically activated water stream and ultrasonic bath immersion cleaning of railhead leaf-film contaminant](#)

L R Goodes, T J Harvey, N Symonds et al.

[Bioinspiration---the solution for biofouling control?](#)

Emily Ralston and Geoffrey Swain

[Miniaturized rotating disc rheometer test for rapid screening of drag reducing marine coatings](#)

Simon Dennington, Ponkrit Mekkhunthod, Martin Rides et al.

[Characterization and anti-settlement aspects of surface micro-structures from Cancer pagurus](#)

T Sullivan, K McGuinness, N E O' Connor et al.

[1,2,3-Triazole/MWCNT conjugates as filler for gelcoat nanocomposites: new active antibiofouling coatings for marine application](#)

Daniela Iannazzo, Alessandro Pistone, Annamaria Visco et al.

[The characterization, replication and testing of dermal denticles of S. canicula](#)

Timothy Sullivan and Fiona Regan

# Surface Topography: Metrology and Properties



## PAPER

### Bubbles versus biofilms: a novel method for the removal of marine biofilms attached on antifouling coatings using an ultrasonically activated water stream

RECEIVED  
2 February 2016

REVISED  
18 July 2016

ACCEPTED FOR PUBLICATION  
3 August 2016

PUBLISHED  
19 September 2016

M Salta<sup>1,6</sup>, L R Goodes<sup>2</sup>, B J Maas<sup>3</sup>, S P Dennington<sup>2</sup>, T J Secker<sup>4</sup> and T G Leighton<sup>5</sup>

<sup>1</sup> Faculty of Sciences, School of Biological Sciences, University of Portsmouth, Portsmouth, UK

<sup>2</sup> Faculty of Engineering and the Environment, National Centre for Advanced Tribology at Southampton (nCATS), University of Southampton, Southampton, UK

<sup>3</sup> Faculty of Technology, School of Engineering, University of Portsmouth, Portsmouth, UK

<sup>4</sup> Faculty of Natural & Environmental Sciences, Centre for Biological Sciences, University of Southampton, UK

<sup>5</sup> Institute of Sound and Vibration Research, Faculty of Engineering and the Environment, University of Southampton, Southampton, UK

<sup>6</sup> Author to whom any correspondence should be addressed.

E-mail: [maria.salta@port.ac.uk](mailto:maria.salta@port.ac.uk)

**Keywords:** biofilms, adhesion, ultrasonically activated stream, antifouling, coatings, cleaning, method

## Abstract

The accumulation of marine organisms on a range of manmade surfaces, termed biofouling, has proven to be the Achilles' heel of the shipping industry. Current antifouling coatings, such as foul release coatings (FRCs), only partially inhibit biofouling, since biofilms remain a major issue. Mechanical ship hull cleaning is commonly employed to remove biofilms, but these methods tend to damage the antifouling coating and often do not result in full removal. Here, we report the effectiveness of biofilm removal from FRCs through a novel cleaning device that uses an ultrasonically activated stream (UAS). In this device, ultrasound enhances the cleaning properties of microbubbles in a freely flowing stream of water. The UAS was applied on two types of commercial FRCs which were covered with biofilm growth following twelve days immersion in the marine environment. Biofilm removal was quantified in terms of reduction in biovolume and surface roughness, both measured using an optical profilometer, which were then compared with similar measurements after cleaning with a non-ultrasonically activated water stream. It was found that the UAS significantly improves the cleaning capabilities of a water flow, up to the point where no detectable biofilm remained on the coating surfaces. Overall biofilm surface coverage was significantly lower on the FRC coatings cleaned with the UAS system when compared to the coatings cleaned with water or not cleaned at all. When biofilm biomass removal was investigated, the UAS system resulted in significantly lower biovolume values even when compared to the water cleaning treatment with biovolume values close to zero. Remarkably, the surface roughness of the coatings after cleaning with the UAS was found to be comparable to that of the blank, non-immersed coatings, illustrating that the UAS did not damage the coatings in the process.

The data supporting this study are openly available from the University of Southampton repository at <http://dx.doi.org/10.5258/SOTON/399420>.

## Introduction

The unwanted growth of marine organisms on the hulls of ships, known as biofouling, is a well-known phenomenon with serious economic consequences. The attachment of plants and animals such as seaweed (algae) and barnacles causes a great increase in

frictional drag, resulting in increased fuel consumption with correspondingly higher emissions of carbon and sulphur dioxides. The significant impact of biofilms on a ship hull's surface roughness, and therefore drag, has been repeatedly reported (e.g. Schultz 2004, Schultz 2007). Recent findings by Schultz *et al* (2015) demonstrated that biofilms were

responsible for an up to 70% increase in skin-friction when they tested FRC systems with biofilm thickness up to  $\sim 500 \mu\text{m}$ . As the global oceangoing fleet was calculated to consume between 200 and 290 million tonnes of fuel in the year 2000 (Eyring *et al* 2010), this level of drag results in the annual wastage of fuel costing billions of dollars.

Throughout history various poisonous compounds have been applied to ships below the waterline to kill and deter biofouling organisms. These have often had deleterious effects on the environment. From the 1970s onwards many ships were coated with antifouling paint containing organotin (primarily tributyltin) compounds. These extremely toxic compounds were very successful at preventing biofouling but also killed many non-target species in harbours and coastal waters resulting in a ban on their use in 2003 and a total ban of their presence in 2008 by the International Maritime Organisation (IMO) (2009).

Over the past couple of decades a new technology for marine antifouling called foul release coatings (FRCs) has been developed. FRCs are non-toxic and reduce biofouling by having 'non-stick' surfaces with low surface energy. These coatings are mainly based on silicones but may also contain fluoropolymers or hydrogels (Chambers *et al* 2006). FRCs are effective against macrofouling organisms such as algae and barnacles, as these large organisms cannot attach themselves strongly to the surface and are therefore removed by hydrodynamic forces when the ship is underway at moderate speed in the region of 10 knots or more (Swain 1999). The low energy, hydrophobic surfaces of FRCs are however easily colonised by biofilms (Schultz *et al* 2011), which consist largely of bacteria and microalgae (diatoms) with pennate diatoms dominating (Dobretsov and Thomason 2011, Salta *et al* 2013, Hunsucker *et al* 2014, Schultz *et al* 2015). These biofilms are thin and flat, and are therefore subject to low shear forces by flowing water as they may not protrude far beyond the boundary layer. They remain attached to the hull of a ship even at higher speeds and accumulated slime must be physically removed at intervals.

The device of choice for removing biofouling during dry-docking is the power washer (also known as the 'pressure washer'). This method is effective as the high rate of flow induces pressure and shear onto the surface to be cleaned (Hagan *et al* 2014). However, high pressure washers may damage the coating, especially FRCs that are particularly sensitive (Bureau of Reclamation 2013). Other drawbacks include the production of backsplash, aerosol and spray, which can carry and redistribute contaminant onto the user (and which can be breathed in) and nearby articles (Leighton *et al* 2013a). The importance of such redistribution depends on the application, and would differ depending on whether the contaminant contained sewage, bacteria, radionucleotides, petrochemicals or

the chemical compounds within marine antifouling coatings.

Outside of dry-docking, the usual way of removing slime coverage is to send divers down with brushes and scrapers whilst the ship is in the water (Hagan *et al* 2014). Increasingly this is not carried out in harbours owing to the problems associated with the large amounts of biofilm and potential alien species released into such confined bodies of water (Minchin and Gollasch 2003). Deploying divers at sea brings problems of logistics and safety. Hull cleaning devices used by divers are normally hydraulically powered units with rotating heads bearing anything from polypropylene bristles to metal scrapers, depending on the degree of biofouling encountered. Mechanical hull cleaning inevitably causes some abrasion, especially to the relatively soft, elastomeric surfaces of FRCs. Damage to antifouling resulting from cleaning by divers using brushes has been estimated to cost US\$6.00 per square metre (ANON 2015). Cleaning systems incorporating cavitation effects in the water flow, induced by the shape of the orifice, were tested almost two decades ago (Kalamuck *et al* 1997) but have not been widely adopted.

We propose to use a newly developed non-abrasive cleaning technology to remove accumulated biofilm from a ship's hull: an Ultrasonically Activated Stream (UAS) technology. The UAS system was invented and developed at the University of Southampton (Leighton *et al* 2016) and is being commercialised under licence by Ultrawave Ltd. The UAS system uses ultrasound to excite endogenous bubbles in a moderately flowing stream of water ( $1\text{--}2 \text{ l min}^{-1}$ ). This allows the removal of persistent contaminants without the necessity of chemical reagents that would otherwise be used to enhance cleaning. The ultrasonically activated bubbles are attracted and particularly effective at penetrating into cracks and crevices and lifting contaminants from the surface topography (Offin *et al* 2014, Birkin *et al* 2015a, 2015b, Birkin *et al* 2016).

Ultrasonic cleaning by UAS has properties, and provides useful facilities, which are wholly distinct from the form of ultrasonic cleaning that has been conducted for decades, for example, in ultrasonic cleaning baths (Leighton *et al* 2005, Rivas and Verhaagen 2016). The ability of ultrasonic cleaning baths (and related laboratory equipment, the sonochemical reaction vessel and the ultrasonically-equipped bioreactor) to remove biofouling from targets small enough to fit in baths has been tested (Zips *et al* 1990, Wang *et al* 2009). Perhaps most obviously, UAS does not require immersion of the target to be cleaned, which restricts bath cleaning to components small enough to be contained within the bath (Mazue *et al* 2011, Legg *et al* 2015). Such immersion can disturb the acoustic field that is set up in a bath, and reduce its cleaning ability (Leighton *et al* 2013a) because slight changes to the container and volume within it can disturb a tuned field and reduce its amplitude


(Birkin *et al* 2003). UAS is immune to this drawback (Goodes *et al* 2016). Moreover, UAS does not expose cleaned items to the 'soup' of contaminants that can be present in a used ultrasonic bath (Leighton 2015), which can have implications for secondary contamination. Furthermore, UAS has been found to cause no damage to delicate surfaces (e.g. baby salad leaves) that would suffer when placed in an ultrasonic cleaning bath: this is because UAS cleans using only shear forces, and does not generate cleaning by stimulating inertial cavitation on the surface to be cleaned (the mechanism by which all prior ultrasonic cleaning techniques work), and so avoids blast waves, bubble jetting, and the production of free radicals. Further details are given in the next section.

The device has been successfully tested against biofilm formed of the medically important bacterium *S. epidermidis* (Birkin *et al* 2015a) in which the UAS removed ~97% of the biomass, which was about 3 times the amount removed by the flow of water alone. The technology also proved effective at removing dental biofilms (plaque) composed of three different species of bacterium (Howlin *et al* 2015), achieving 99.9% removal of *S. mutans* in 10 s of exposure. Therefore it was of interest to test whether an UAS could be used to remove marine biofilms formed on commercial FRCs during exposure in the sea, and whether the UAS would cause any damage to the soft surface of such coating. The aim of the current work is to evaluate the effectiveness of this new cleaning method for the removal of biofilms formed on FRCs.

## Materials and methods

### Experimental rig and coatings

Two types of commercial FRCs were tested, referred to as FRC 1 and FRC 2. FRC1 is a modified silicone polymer coating, the hydrophobic surface of which develops a hydrophilic character on immersion in water. FRC2 is a fluoropolymer-based coating also with a moderately hydrophilic surface. Both coatings are smooth, relatively soft and elastomeric. These were applied on standard laboratory glass slides (Fisher Scientific) by the coating manufacturer. The coated slides were then mounted on custom-built experimental rosettes which each accommodate up to eight glass-slide-shaped surfaces (Meier *et al* 2013). The design of the experimental rosette can be seen in figure 1. In total, five duplicate coatings for each FRC were immersed in the sea at 1 m depth in June 2014 for 12 d, at a pontoon located at the National Oceanography Centre, Southampton, UK. Southampton is characterised by a temperate climate and June is a biofouling-intense month where increased biological activity is normally expected. For blanks, non-immersed FRC1 and FRC2 coatings (three duplicates per FRC) were used.

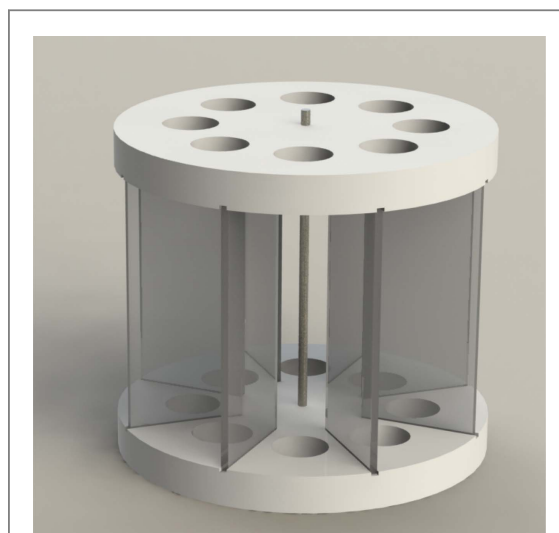

**Figure 1.** SolidWorks version 2013 (Dassault Systèmes, Vélizy-Villacoublay, France) model of the experimental rosette with eight glass slides mounted. The holes in the two holders (top and bottom) facilitate flow through the rosette.

### Cleaning system and experimental procedure

The cleaning system that was assessed uses an UAS. In the UAS prototype that was used for this study, the water running through the device is ultrasonically stimulated before leaving its 1 cm diameter nozzle (the system is fully described in Birkin *et al* 2015a). Rather than pressurising the stream (the prototype exerts pressures of less than 100 Pa on the surface to be cleaned, compared to 5–200 MPa for pressure washers), the ultrasonic stimulation causes surface waves to propagate on the bubbles-of-opportunity that are naturally present in the water supply (Maksimov and Leighton 2001, Maksimov and Leighton 2011). This is a phenomenon that occurs in presence of an acoustic field with the correct combination of frequency and amplitude (Birkin *et al* 2002). The ultrasonically activated bubbles cause local convection and shear forces in the water surrounding the bubbles (Watson *et al* 2003), mechanically enhancing the capability of the water stream to remove contaminants (Leighton 2004, Howlin *et al* 2015, Birkin *et al* 2015a, 2015b, Birkin *et al* 2016). The ultrasonic activation furthermore forces the bubbles into any cracks and crevices that may exist in the surface that is to be cleaned, performing even within contours that are difficult to reach with conventional cleaning devices such as wipes and brushes (Leighton 2015).

Although UAS systems can be made to work with chemicals such as surfactants, the prototype was here used without any additives. The device normally operates directly from mains water supply, but because the experiment was not executed in the vicinity of the mains water supply, the system was configured to run from a recirculating additive-free water stream originating from the mains. As the rippling stimulated on the surface of the bubbles is of a far lower energy level

than the inertial cavitation that can be generated from intense ultrasound, phenomena associated with such cavitation such as the generation of free radicals, luminescence and shock waves do not occur (Leighton *et al* 1988, 2008, Birkin *et al* 2005a, 2005b, Turangan *et al* 2008). The regime of non-inertial cavitation that UAS produces at the surface to be cleaned is one where the bubble is driven by the acoustic field to undergo small amplitude pulsations, corresponding to the zeroth order spherical harmonic perturbation. In UAS this pulsation in turn also excites the high order spherical harmonic perturbations, generating the surface ripples on the bubble wall and the shear and convection associated with UAS cleaning.

In this regime of non-inertial cavitation, the position and motion of the bubble wall are determined by the usual balance between inertia and stiffness found in an oscillator undergoing small amplitude oscillation. In a bubble, the inertia is associated with the dense liquid and the stiffness with the compressible gas. This balance determines the pulsation resonance for small amplitude oscillations, but it is a balance that breaks during the large amplitude bubble pulsations that characterise inertial cavitation (the phenomenon used by all other ultrasonic cleaning systems). During inertial cavitation, the bubble expands to many times its original size, and then as the bubble contracts the inertial forces associated with the liquid dominate the motion so substantially that the stiffness of the gas/vapour liquid in the bubbles plays no significant role in determining the motion of the bubble wall (Leighton *et al* 2000). In cleaning processes, the bubble loses sphericity, the bubble can involute to form a jet, and the collapse ends in a liquid/liquid impact which releases a blast wave into the liquid (Leighton *et al* 2013b). The compressed gas momentarily achieves high temperatures (which can generate free radical, Birkin *et al* 2001), but the absolute amount of energy contained in the gas is tiny. The jetting and blast wave can generate physical damage (Birkin *et al* 2004), particularly as crevices in the target to be cleaned can focus stress and become enlarged (Jamaluddin *et al* 2011).

Although the use of UAS has in common parlance been likened to 'placing an ultrasonic cleaning bath at the end of a water stream', it differs in two important aspects, the first being the manner of the bubble activity as described. The second is the fact that traditional ultrasonic cleaning baths limit the size of the object to be cleaned, as it has to be able to fit into the bath; this does not occur with UAS which in such circumstances outclasses the ultrasonic cleaning bath in performance (Goodes *et al* 2016). Goodes *et al* (2016) furthermore demonstrated that UAS can clean a contaminant that an ultrasonic cleaning bath failed to remove, even though UAS has also cleaned delicate surfaces that would be severely damaged in an ultrasonic cleaning bath without damaging them, due to the fact that that



the mechanism by which UAS operates is very different from traditional ultrasonic cleaning.

In order to quantify the cleaning performance of the UAS prototype on fouled FRC coatings, the coatings were exposed to the UAS as well as a similar water flow (WTR) in absence of ultrasonic activation. The control flow originates from the same device, the only difference being that the acoustic field is turned off. In both cases, the coatings were exposed in the laboratory to a flow of  $2 \text{ l min}^{-1}$  for 30 s at a 5 mm distance from the nozzle targeting a single spot for each cleaning area ( $25 \text{ cm} \times 25 \text{ cm}$ ), as seen in figure 3. In the same figure (3) it can be seen that each coating was separated in three parts, where each was either cleaned with the UAS system, WTR or non-cleaned ( $25 \text{ cm} \times 25 \text{ cm}$  each area). The edges of the slides were avoided from the analysis to avoid bias and artefacts. A total of five replicated coatings were tested for each FRC, where one side was cleaned using UAS and the other side of the same coating was tested with non-activated water (see figure 3).

#### Surface roughness, biovolume removal measurements and biofilm surface coverage

The control and UAS-cleaned FRC surfaces were analysed using an Alicona InfiniteFocus G4 focus variation optical profilometer. Objective lenses were selected for analysis of a suitable sample area size, and roughness was assessed in those areas, according to ISO25178 recommendations. This generates a fully focussed optical image in the sample area, as well as determines the axial location of features, allowing derivation of 2D or 3D roughness data. Magnifications were selected from a range of 10x, 20x and 50x objective lenses as appropriate for the height of features in the selected area, as directed by the ISO and manufacturer guidelines. For the purpose of this study, 3D roughness parameters ( $S_a$ , the arithmetic average of the 3D roughness) were assessed as befits the random, heterogeneous and non-directional nature of the fouling present on the surface. The results of the biovolume measurements are expressed in terms of their relative layer thickness (in  $\mu\text{m}^3 \mu\text{m}^{-2}$ ), which is calculated by dividing the total biovolume ( $\mu\text{m}^3$ ) by the area over which it is divided ( $\mu\text{m}^2$ ). For each of the two parameters measured (surface roughness and biovolume), nine images were acquired ( $N = 9$  per coating, per cleaning treatment).

To quantify biofilm presence/absence at the macroscale, ImageJ (MacBiophotonics ImageJ, USA) images with the entire slides were measured for percentage of biofilm surface coverage. Images from cleaned (WTR or UAS) and non-cleaned (before) sections from the slide (approximately  $25 \times 25 \text{ cm}$  each) converted into a binary format (i.e. pixel value was either 0 or 255) and covered areas (i.e. surface areas with biofilm) were quantified ( $N = 18$  measurements per treatment i.e. 18 for water, 18 for UAS, 18 before for

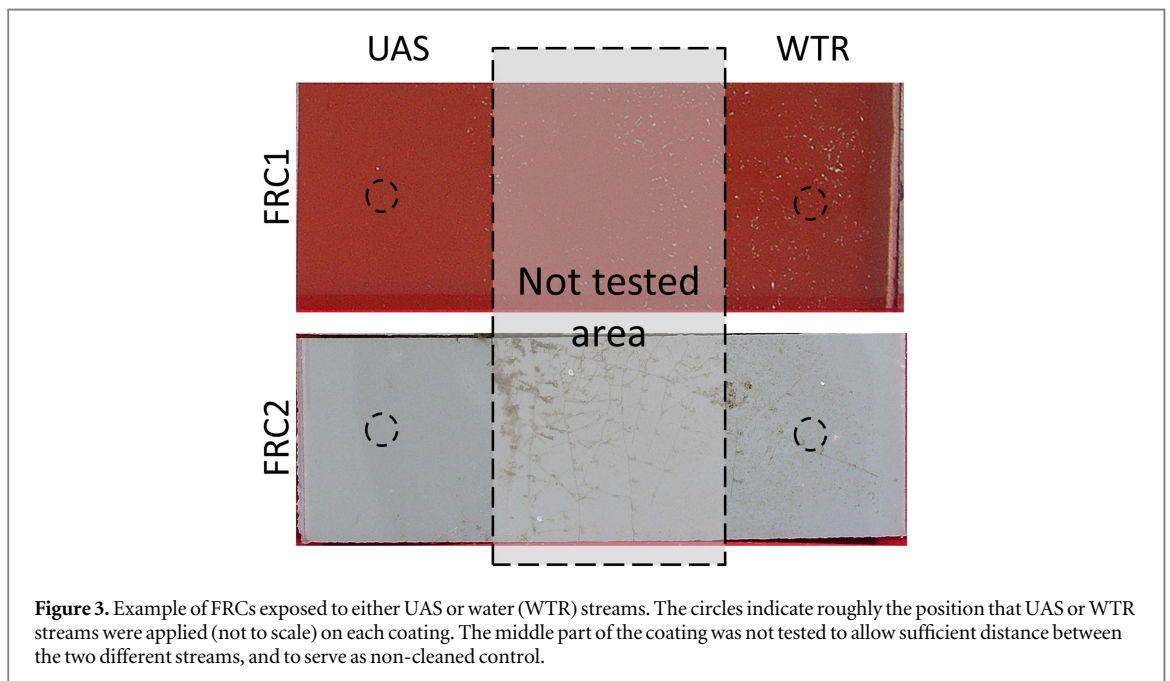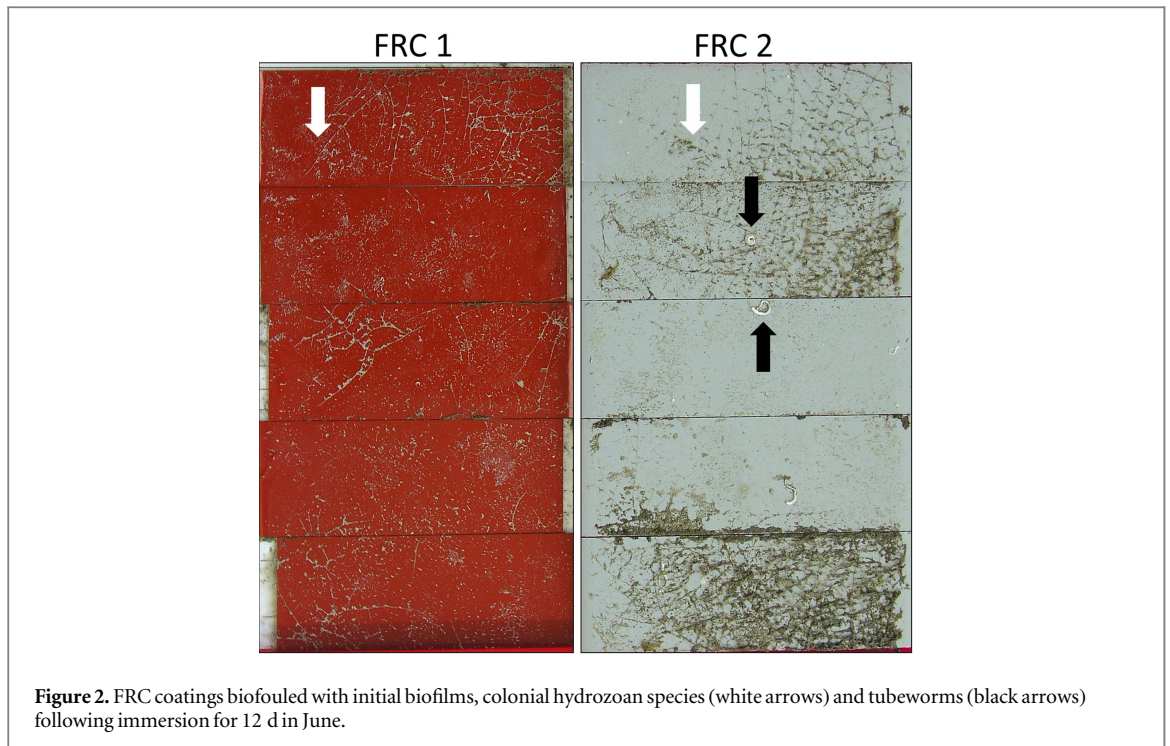

each FRC type). To test for differences between the coatings following cleaning treatments, a Mann-Whitney statistical test was utilised using Matlab version R2015a (MathWorks, Natick, MA, USA).



## Results

### Coating performance

Following 12 days of continuous immersion, the two FRC systems have been colonised with both biofilms (slime) and macrofouling (colonial hydrozoans and tubeworms), as seen in figure 2. Figure 3 illustrates

an example of post-cleaning with WTR and UAS for both FRCs, where there is a clear visual difference in cleaning efficiency with UAS resulting in clean surfaces.

When biofilm formation on the FRCs was measured in terms of overall biofilm surface coverage, it was found that the area where the UAS was applied (approximately 24 cm × 25 cm) had almost no apparent biofilm left when compared to the non-cleaned areas (Before) and the areas cleaned with water (WTR) (figure 4). Specifically, following statistical analysis, biofilm surface coverage was found to be significantly lower on the FRC1 coatings cleaned with

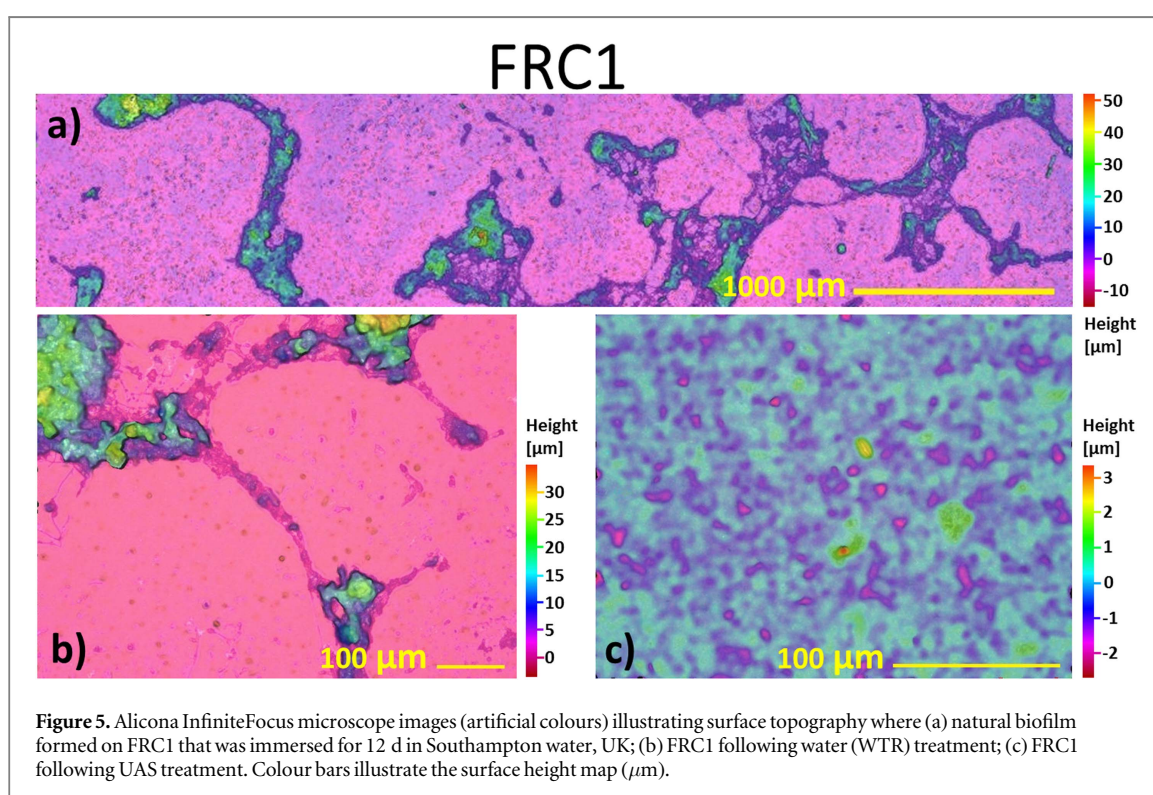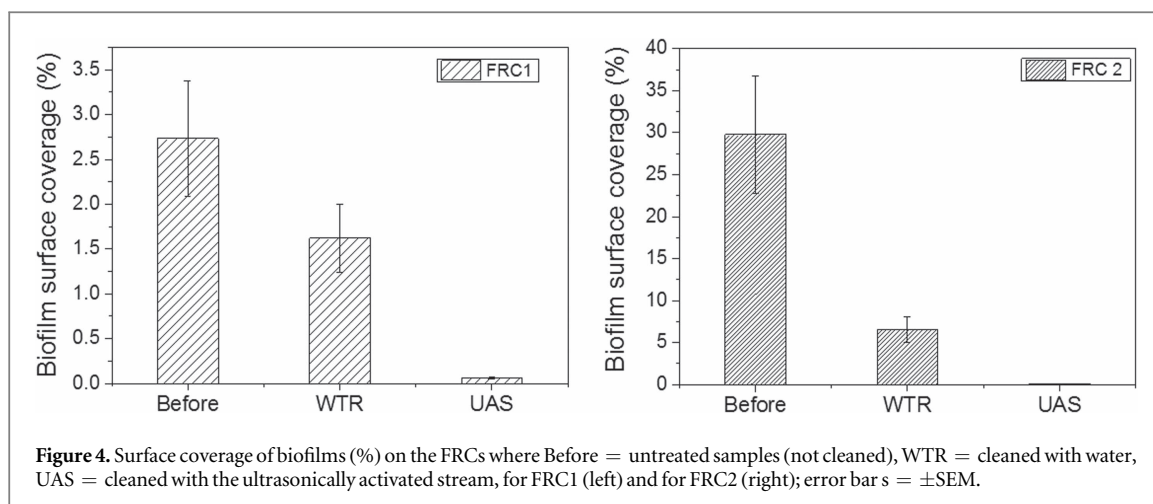



water (WTR) and the UAS system when compared to the non-cleaned (Before) area, with  $p < 0.010$  and  $p < 0.001$ , respectively. When comparing biofilm surface coverage on coating cleaned with the UAS and WTR, it was found that the UAS part had almost non biofilm present ( $p < 0.001$ ). The exact same was evident for the FRC2 system when biofilm surface coverage on the non-cleaned (Before) area of the coating had significantly higher coverage when compared to the WTR and UAS cleaned areas ( $p < 0.001$  for both). Yet again, when comparing the WTR cleaned with the UAS cleaned areas, there is significantly less (almost non-existent) biofilm present on the coating area cleaned with the UAS ( $p < 0.001$ ).

Figures 5 and 6 illustrate the surface topography of FRC1 and FRC2, respectively; a substantial biofilm is formed on both FRC systems. However, FRC2

(figure 6(a)) is characterised by higher biological activity that includes a substantially grown and complex macrofouling layer that reaches 700  $\mu$ m in thickness, as opposed to 40  $\mu$ m for the FRC1. The water treatment shows a more profound effect for FRC2 with peak thickness being reduced down to approximately 16  $\mu$ m (figure 6(b)), while the effect of the same treatment is less obvious on FRC1 (figure 5(b)). The obvious removal of biofilm with the UAS system can be clearly seen for both FRCs since in both cases the peak thickness is reduced down  $\sim 3$ –4  $\mu$ m (figures 5(c) and 6(c)).

#### Surface roughness and biomass removal by UAS

The effect of the UAS system on biofilm removal can be seen in figure 7. In good agreement with the surface topography images, the water (WTR) cleaning method

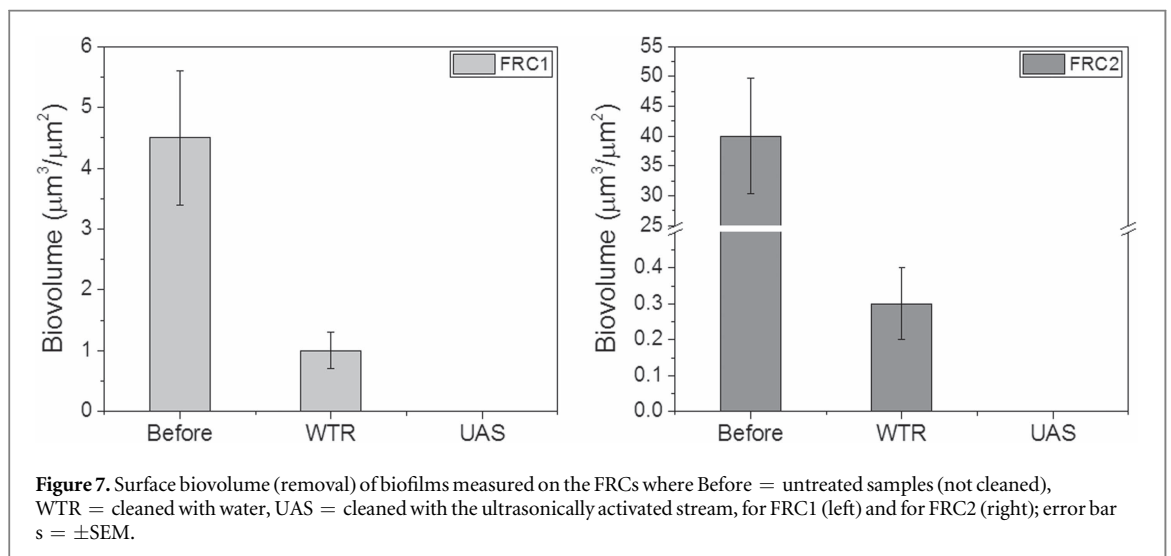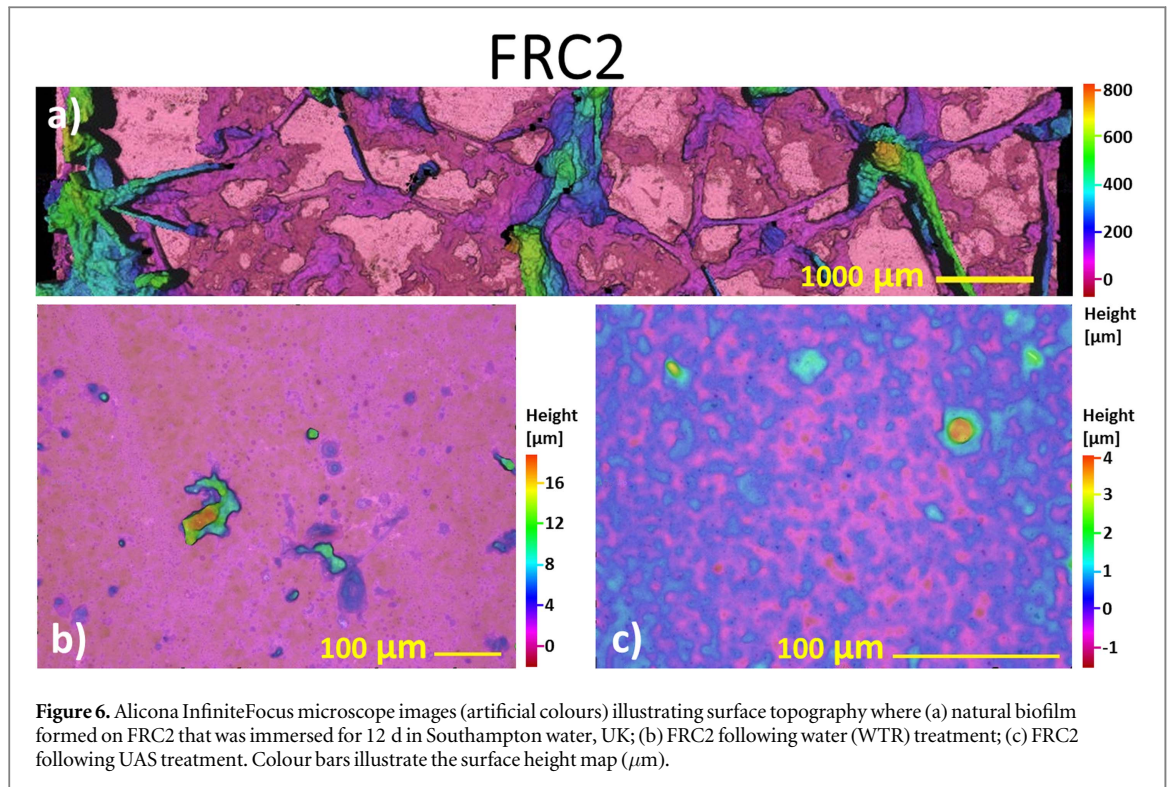

resulted in significant biofilm removal for both FRCs (figure 7, Before versus WTR: FRC1,  $p < 0.01$ ; FRC2,  $p < 0.01$ ), however still leaving traces of thin biofilms on the coatings. Remarkably, the UAS system resulted in significantly lower biovolume values even when compared to the WTR cleaning treatment (figure 7, WTR versus UAS:  $p < 0.01$  for FRC1 and FRC2) with biovolume values close to zero (average biovolume for FRC1 =  $0.001 \mu\text{m}$  and for FRC2 =  $0.010 \mu\text{m}$ ).


Equally, surface roughness was significantly decreased when WTR cleaning treatment was used on both FRCs (figure 8, Before versus WTR:  $p < 0.01$  for FRC1 and FRC2). For FRC1, the surface roughness after UAS cleaning was even further reduced when compared to the WTR cleaning (figure 8(a),

$p < 0.01$ ). Importantly, when blank FRCs (i.e. non-immersed) were compared with the fouled FRCs after both WTR and UAS treatments, there was no significant difference between the UAS and the blanks (FRC1,  $p = 1.00$ ; FRC2,  $p = 0.24$ ) although there was a significant difference between the WTR and the blanks ( $p < 0.01$  for FRC1 and FRC2). This illustrates that only following cleaning with UAS, the surface roughness of the FRCs was reduced to levels similar as those prior immersions in the sea.

## Discussion

In the current work, for the first time, we report that the UAS system completely removed detectable



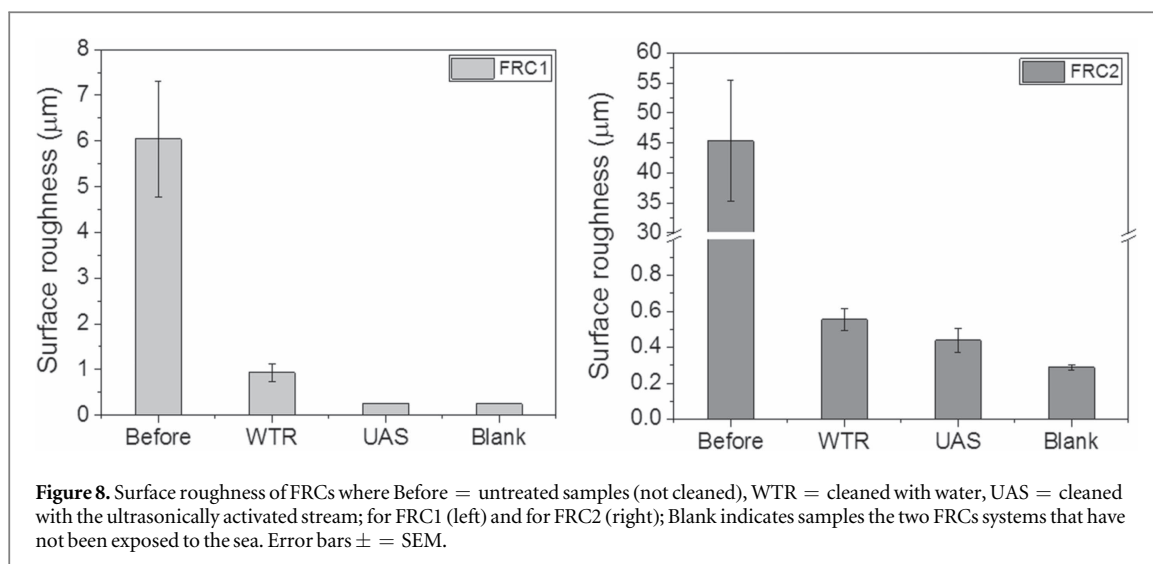

**Figure 8.** Surface roughness of FRCs where Before = untreated samples (not cleaned), WTR = cleaned with water, UAS = cleaned with the ultrasonically activated stream; for FRC1 (left) and for FRC2 (right); Blank indicates samples the two FRCs systems that have not been exposed to the sea. Error bars  $\pm$  = SEM.

marine biofilms from two types of FRCs. Measurements showed that the surface roughness of the fouled coatings was reduced from 6.05 to 0.25  $\mu\text{m}$  for FRC1 and from 45.32 to 0.44  $\mu\text{m}$  for FRC2 following UAS cleaning. Importantly, the surface roughness values after the UAS cleaning proved to be directly comparable to those of the blank, non-fouled coatings (0.25  $\mu\text{m}$  for FRC1 and 0.29  $\mu\text{m}$  for FRC2). This indicates first of all the high effectiveness of the UAS system against natural biofilms, but also shows that the cleaning is achieved without damaging the coating itself. The indication that the UAS cleaning is non-damaging to the FRCs is an important improvement to conventional high-pressure water blast cleaning methods for ship hulls (typically at a pressure of 20–60 MPa). In a study where FRCs were tested against a high-pressure cleaning system, it was found that the pressure from water jetting gives rise to intense pressure fluctuations from cavitation, leading to either small hole formation on the coatings or the complete removal of the coating in large pieces (Bureau of Reclamation 2013).

In previous studies, increase in ship hull drag due to biofouling was measured over a period of two years and it was found to have increased by 35% by the end of that period (Kane 2012). Interestingly, following a conventional full hull brush cleaning, the drag showed only a 10% decrease with pre-cleaning conditions. On top of that, silicone based coatings like FRCs are fragile and therefore intrusive cleaning methods, such as the traditional stiff rotating brushes, may damage these soft coatings (Baier et al 1997, Christiaen 1998, Holm et al 2003) and impede their overall performance (Baier et al 1997). Similar conclusions could be valid for other types of antifouling coatings like those that are loaded with booster biocides, such as copper, which are particularly toxic when released into the environment in an uncontrolled manner. Copper, in concentrations as low as a few  $\mu\text{g l}^{-1}$ , may impede

photosynthesis in algae and interfere with enzyme function in both algae and animals (Yruela 2005), and aggressive cleaning methods may lead to abrasion with elevated release of booster biocides (Valkirs et al 1994, Bohlander and Montemarano 1997). Although the UAS system was not tested against biocide-containing coatings here, potentially successful results of this non-abrasive cleaning method would eliminate the issue of biocide release into the environment.

The biovolume results also prove the UAS system to be particularly successful; before cleaning with the UAS the measured biovolume was found to be 4.52  $\mu\text{m}^3 \mu\text{m}^{-2}$  and 39.00  $\mu\text{m}^3 \mu\text{m}^{-2}$  for FRC1 and FRC2, respectively. Following cleaning with the UAS system, these values were markedly reduced to 0.00  $\mu\text{m}^3 \mu\text{m}^{-2}$  for FRC1 and 0.01  $\mu\text{m}^3 \mu\text{m}^{-2}$  for FRC2. When the FRCs were cleaned with the non-ultrasonically activated water stream, the biovolume was reduced to a significantly less extent reaching 1.01  $\mu\text{m}^3 \mu\text{m}^{-2}$  and 0.30  $\mu\text{m}^3 \mu\text{m}^{-2}$  for FRC1 and FRC2, respectively. Surface cleaning through the use of water hosing or jetting to remove biofilms is a typically used process which has been often problematic and cost effective. The degree of biofilm removal of *Pseudomonas aeruginosa* using a range of water pressures, water temperatures (cold versus hot) and chemical (surfactant) addition has been previously assessed and it was found that despite the combination of all three parameters, biofilm reduction was partially observed, however removal was not achieved (Gibson et al 1999, Burfoot and Middleton 2009). The proposed cleaning method via the UAS system is thus very promising for a number of industries where cleaning with water alone is of importance.

Recent efforts towards the development of environmentally friendly antifouling coatings have focused on bio-inspired approaches with the most common being the reproduction of complex surface topographies often encountered on the skins or shells of

marine organisms (Bers and Wahl 2004, Bers et al 2010, Salta et al 2010, Scardino and de Nys 2011). These bio-inspired coatings are primarily made of soft materials such as silicones (polydimethylsiloxane), which are prone to damage, like the FRC systems, and therefore would greatly benefit from a non-abrasive cleaning method such as the UAS. Furthermore, these topographies often supply niches for biofilm forming species to anchor on (Scardino et al 2006), which are difficult to reach with conventional cleaning methods. The acoustic field of the UAS method causes its bubbles to infiltrate and effectively clean micro structures that normal water streams would fail to reach (Leighton 1994, Offin et al 2014). In that respect, topographically enhanced coatings would benefit from the UAS cleaning technique on multiple levels, making the bio-inspired antifouling approaches especially efficacious.

Despite enhanced efforts to discover an environmentally friendly and cost effective coating that will have a permanent antifouling effect, no such coating is currently available and biofilm accumulation on marine industrial settings such as ship hulls but also water pipes, hydro-acoustic systems and reverse osmosis membranes (for water desalination) remains an ongoing issue. Therefore, a cleaning method that will allow complete biofilm removal is desirable and indeed crucial. The current work has demonstrated some very promising results, with naturally occurring detectable biofilms being fully removed from commercially available FRCs using the UAS system. Future experiments will focus on testing the UAS cleaning efficiency on different types of antifouling coatings, such as ones containing booster biocides and topographically enhanced surfaces. If the promising results of the current work are sustained, cleaning using ultrasonically activated bubbles may become a standard method in marine biofilm removal.

## Acknowledgments

The project benefited from the loan of equipment developed for AntiMicrobial Resistance studies by NAMRIP under EPSRC's Network for Antimicrobial Action, 'Bridging the Gap' programme grant NAMRA (EP/M027260/1). All data supporting this study are openly available from the University of Southampton repository at <http://dx.doi.org/10.5258/SOTON/399420>.

## References

- ANON 2015 Ship Repair and Conversion Technology, 1st Quarter 2015, retrieved from (<http://umc-int.com/media/54677/Q1-ship-repair-article.pdf>)
- Baier R, Meyer A and Forsberg R 1997 Certification of properties of nontoxic fouling-release coatings exposed to abrasion and long-term immersion *Nav. Res. Rev.* **49** 60–5
- Bers A, Diaz E, Da Gama B, Vieira-Silva F, Dobretsov S, Valdivia N, Thiel M, Scardino A, McQuaid C and Sudgen H 2010 Relevance of mytilid shell microtopographies for fouling defence—a global comparison *Biofouling* **26** 367–77
- Bers A and Wahl M 2004 The influence of natural surface microtopographies on fouling *Biofouling* **20** 43–51
- Birkin P et al 2015a Cold water cleaning of brain proteins, biofilm and bone—harnessing an ultrasonically activated stream *Phys. Chem. Chem. Phys.* **17** 20574–9
- Birkin P, Offin D, Vian C and Leighton T 2015b Electrochemical 'bubble swarm' enhancement of ultrasonic surface cleaning *Phys. Chem. Chem. Phys.* **17** 21709–15
- Birkin P R, Offin D G, Joseph P F and Leighton T G 2005b Cavitation, shock waves and the invasive nature of sonoelectrochemistry *J. Phys. Chem. B* **109** 16997–7005
- Birkin P R, Offin D G and Leighton T G 2004 Electrochemical measurements of the effects of inertial acoustic cavitation by means of a novel dual microelectrode *Electrochem. Commun.* **6** 1174–9
- Birkin P R, Offin D G and Leighton T G 2005a Experimental and theoretical characterisation of sonochemical cells: 2. Cell disruptors (Ultrasonic horns) and cavity cluster collapse *Phys. Chem. Chem. Phys.* **7** 530–7
- Birkin P R, Offin D G and Leighton T G 2016 An activated fluid stream—new techniques for cold water cleaning *Ultrason. Sonochem.* **29** 612–8
- Birkin P R, Power J F and Leighton T G 2001 Electrochemical evidence of H<sup>•</sup> produced by ultrasound *Chem. Commun.* 2230–1
- Birkin P R, Power J F, Vinçotte A M and Leighton T G 2003 A 1 kHz resolution frequency study of a variety of sonochemical processes *Phys. Chem. Chem. Phys.* **5** 4170–4
- Birkin P R, Watson Y E, Leighton T G and Smith K L 2002 Electrochemical detection of Faraday waves on the surface of a gas bubble *Langmuir* **18** 2135–40
- Bohlander G 1997 Biofouling, fleet maintenance and operational needs *Nav. Res. Rev.* **44** 9–17
- Bureau of Reclamation 2013 Resistance of Protective Coatings to High Pressure Water Jets for Invasive Mussel Removal. Hydraulic Laboratory Technical Memorandum PAP-1074. Retrieved from ([https://usbr.gov/research/projects/download\\_product.cfm?id=700](https://usbr.gov/research/projects/download_product.cfm?id=700))
- Burfoot D and Middleton K 2009 Effects of operating conditions of high pressure washing on the removal of biofilms from stainless steel surfaces *J. Food Eng.* **90** 350–7
- Chambers L D, Stokes K R, Walsh F C and Wood R J K 2006 Modern approaches to marine antifouling coatings *Surf. Coat. Technol.* **201** 3642–52
- Christiaen A-C 1998 Evaluation of the durability of elastomeric easy-release coatings *PhD Thesis* Virginia Polytechnic Institute and State University, Blacksburg
- Dobretsov S and Thomason J C 2011 The development of marine biofilms on two commercial non-biocidal coatings: a comparison between silicone and fluoropolymer technologies *Biofouling* **27** 869–80
- Eyring V, Isaksen I S, Berntsen T, Collins W J, Corbett J J, Endresen O, Grainger R G, Moldanova J, Schlager H and Stevenson D S 2010 Transport impacts on atmosphere and climate: shipping *Atmos. Environ.* **44** 4735–71
- Gibson H, Taylor J, Hall K and Holah J 1999 Effectiveness of cleaning techniques used in the food industry in terms of the removal of bacterial biofilms *J. Appl. Microbiol.* **87** 41–8
- Goodes L R, Harvey T, Symonds N and Leighton T G 2016 A comparison of ultrasonically activated water stream and ultrasonic bath immersion cleaning of railhead leaf-film contaminant *Surf. Topogr.: Metrol. Prop.* **4** 034003
- Hagan P, Price E and King D 2014 Status of Vessel Biofouling Regulations and Compliance Technologies *Economic Discussion Paper* 14-HF-01 Maritime Environmental Resource Center (MERC) [www.maritime-enviro.org/Downloads/Reports/Other\\_Publications/Status\\_of\\_Vessel\\_Biofouling\\_Regs\\_2014\\_%20Nov\\_18\\_2014.pdf](http://www.maritime-enviro.org/Downloads/Reports/Other_Publications/Status_of_Vessel_Biofouling_Regs_2014_%20Nov_18_2014.pdf)
- Holm E R, Haslbeck E G and Horinek A A 2003 Evaluation of brushes for removal of fouling from fouling-release surfaces, using a hydraulic cleaning device *Biofouling* **19** 297–305

- Howlin R P *et al* 2015 Removal of dental biofilms with an ultrasonically activated water stream *J. Dental Res.* **94** 1303–9
- Hunsucker K Z, Koka A, Lund G and Swain G 2014 Diatom community structure on in-service cruise ship hulls *Biofouling* **30** 1133–40
- IMO—International Maritime Organization 2009 Maritime Knowledge Centre. 2009 International shipping and world trade: facts and figures ([http://imo.org/includes/blastData.asp/doc\\_id=12079](http://imo.org/includes/blastData.asp/doc_id=12079))
- Jamaluddin A, Ball G, Turangan C and Leighton T 2011 The collapse of single bubbles and approximation of the far-field acoustic emissions for cavitation induced by shock wave lithotripsy *J. Fluid Mech.* **677** 305–41
- Kalumuck K M, Chahine G S and Aley P D 1997 Development of a DynaJet™ cavitating water jet cleaning tool for underwater marine fouling removal *9th American Waterjet Conf.* vol 39 (Dearborn, Michigan, USA) pp 541–54
- Kane D 2012 Evaluating hull fouling on ship performance: underwater photos in connection with speed/fuel consumption analysis *16th Int. Conf. on Marine Corrosion and Fouling (Seattle, Washington, USA)*
- Legg M, Yücel M, de Carellan I G, Kappatos V, Selcuk C and Gan T 2015 Acoustic methods for biofouling control: a review *Ocean Eng.* **103** 237–47
- Leighton T 1994 *The Acoustic Bubble* (New York: Academic) p 640
- Leighton T 2004 From seas to surgeries, from babbling brooks to baby scans: the acoustics of gas bubbles in liquids *Int. J. Mod. Phys. B* **18** 3267–314
- Leighton T, Birkin P, Hodnett M, Zeqiri B, Power J, Price G, Mason T, Plattes M, Dezhkunov N and Coleman A 2005 Characterisation of measures of reference acoustic cavitation (COMORAC): an experimental feasibility trial *Bubble and Particle Dynamics in Acoustic Fields: Modern Trends and Applications* ed A A Doinikov (Kerala: Research Signpost) pp 37–94
- Leighton T, Cox B and Phelps A 2000 The Rayleigh-like collapse of a conical bubble *J. Acoust. Soc. Am.* **107** 130–42
- Leighton T, Fedele F, Coleman A, McCarthy C, Ryves S, Hurrell A, De Stefano A and White P 2008 A passive acoustic device for real-time monitoring of the efficacy of shockwave lithotripsy treatment *Ultrasound Med. Biol.* **34** 1651–65
- Leighton T, Pickworth M, Walton A and Dendy P 1988 Studies of the cavitation effects of clinical ultrasound by sonoluminescence: 1. Correlation of sonoluminescence with the standing wave pattern in an acoustic field produced by a therapeutic unit *Phys. Med. Biol.* **33** 1239–48
- Leighton T G 2015 The acoustic bubble: oceanic bubble acoustics and ultrasonic cleaning *Proc. Meetings Acoust., Acoust. Soc. Am.* **24** 070006
- Leighton T G, Birkin P and Offin D 2013a A new approach to ultrasonic cleaning *Proc. Meetings Acoust.* **19** 075029
- Leighton T G, Turangan C, Jamaluddin A, Ball G and White P 2013b Prediction of far-field acoustic emissions from cavitation clouds during shock wave lithotripsy for development of a clinical device *Proc. R. Soc. A* **469** 20120538
- Leighton T G, Vian C J B and Birkin P R 2016 Cleaning apparatus and method, and monitoring thereof, European Patent Number 2470310 (granted on 06/01/2016) from Application Number 10748081.6 (filed on 24 February 2012 with an allocated filing date on 26 August 2010) Published 04 July 2012 under 2470310. Claiming priority from GB 0914836.2 and PCT/EP2010/062448. From UK Patent Application No. 0914836.2 (University of Southampton 2009, filed 26 August 2009, published 26 August 2010)
- Maksimov A and Leighton T 2001 Transient processes near the acoustic threshold of parametrically-driven bubble shape oscillations *Acta Acust. United Acust.* **87** 322–32
- Maksimov A and Leighton T 2011 Pattern formation on the surface of a bubble driven by an acoustic field *Proc. R. Soc. Lond. A* **468** 57–75
- Mazue G, Viennet R, Hihn J, Carpentier L, Devidal P and Albaina I 2011 Large-scale ultrasonic cleaning system: design of a multi-transducer device for boat cleaning (20 kHz) *Ultrason. Sonochem.* **18** 895–900
- Meier A, Tsaloglou N-M, Mowlem M C, Keevil C W and Connelly D P 2013 Hyperbaric biofilms on engineering surfaces formed in the deep sea *Biofouling* **29** 1029–42
- Minchin D and Gollasch S 2003 Fouling and ships' hulls: how changing circumstances and spawning events may result in the spread of exotic species *Biofouling* **19** 111–22
- Offin D G, Birkin P R and Leighton T G 2014 An electrochemical and high-speed imaging study of micropore decontamination by acoustic bubble entrapment *Phys. Chem. Chem. Phys.* **16** 4982–9
- Rivas D F and Verhaagen B 2016 Preface to the special issue: cleaning with bubbles *Ultrason. Sonochem.* **29** 517–8
- Salta M, Wharton J, Stoodley P, Dennington S, Goodes L, Werwinski S, Mart U, Wood R and Stokes K 2010 Designing biomimetic antifouling surfaces *Phil. Trans. R. Soc. A* **368** 4729–54
- Salta M, Wharton J A, Blache Y, Stokes K R and Briand J-F 2013 Marine biofilms on artificial surfaces: structure and dynamics *Environ. Microbiol.* **15** 2879–93
- Scardino A, Harvey E and De Nys R 2006 Testing attachment point theory: diatom attachment on microtextured polyimide biomimics *Biofouling* **22** 55–60
- Scardino A J and de Nys R 2011 Mini review: biomimetic models and bioinspired surfaces for fouling control *Biofouling* **27** 73–86
- Schultz M 2004 Frictional resistance of antifouling coating systems *J. Fluids Eng.* **126** 1039–47
- Schultz M 2007 Effects of coating roughness and biofouling on ship resistance and powering *Biofouling* **23** 331–41
- Schultz M, Walker J, Steppe C and Flack K 2015 Impact of diatomaceous biofilms on the frictional drag of fouling-release coatings *Biofouling* **31** 759–73
- Schultz M P, Bendick J A, Holm E R and Hertel W M 2011 Economic impact of biofouling on a naval surface ship *Biofouling* **27** 87–98
- Swain G 1999 Redefining antifouling coatings *J. Protective Coat. Linings* **16** 26–35
- Turangan C, Jamaluddin A, Ball G and Leighton T 2008 Free-lagrange simulations of the expansion and jetting collapse of air bubbles in water *J. Fluid Mech.* **598** 1–25
- Valkirs A, Davidson B, Kear L, Fransham R, Zirino A and Grovhoug J 1994 Environmental effects from in-water hull cleaning of ablative copper antifouling coatings, Naval Command, Control and Ocean Surveillance Center. Technical Document 2662. Retrieved from ([www.dtic.mil/dtic/tr/fulltext/u2/a284381.pdf](http://www.dtic.mil/dtic/tr/fulltext/u2/a284381.pdf))
- Wang Z, Wu Z and Tang S 2009 Extracellular polymeric substances (EPS) properties and their effects on membrane fouling in a submerged membrane bioreactor *Water Res.* **43** 2504–12
- Watson Y E, Birkin P R and Leighton T G 2003 Electrochemical detection of bubble oscillation *Ultrason. Sonochem.* **10** 65–9
- Yruela I 2005 Copper in plants *Braz. J. Plant Physiol.* **17** 145–56
- Zips A, Schaule G and Flemming H 1990 Ultrasound as a means of detaching biofilms *Biofouling* **2** 323–33